

**RATINGS - CHEMICAL EFFECT**

A: No effect - Excellent  
 B: Minor effect - Good  
 C: Moderate effect - Fair  
 D: Severe effect - Not Recommended

	AISI 304	AISI SS316	Titanium	Cast Bronze	Brass	Cast Iron	Carbon Steel	Teflon	Polyethylene	Polypropylene	VITON	BUNA N (Nitrile)	Silicon	Ethylene Propylene (EPDM)
Alcohols Amyl	A	A	A	A	B	C	C	A	B	B	A	A	D	A
Alcohols Benzyl	A	A	A	A	C	-	-	-	D	A	A	D	-	B
Alcohols Ethyl	A	A	A	A	C	A	A	-	B	A	A	A	B	B
Chloric Acid	D	D	-	-	-	-	-	A	-	-	-	D	-	-
Chlorine, Anhydrous Liquid	D	D	D	D	-	C	-	A	D	D	A	D	-	B
Chlorine (dry)	A	A	D	A	B	A	-	A	-	-	D	-	-	-
Chlorine Water	-	D	A	D	D	D	-	A	-	D	A	D	C	-
Chocolate Syrup	A	A	-	-	-	D	-	-	-	A	A	A	-	-
Citric Acid	A	A	A	D	C	D	-	A	B	B	A	D	C	A
Coffee	A	A	-	B	-	C	-	A	-	A	A	A	-	-
Ethyl Chloride	A	A	A	B	-	C	D	A	D	D	A	D	D	A
Ethyl Sulfate	D	-	-	-	-	-	-	-	-	-	A	A	-	-
Ethylene Chloride2	A	A	B	A	-	C	C	A	-	D	A	D	D	C
Ethylene Dichloride	A	A	A	C	-	-	C	A	D	A	A	D	D	C
Ethylene Glycol4	A	A	-	B	B	B	C	A	B	A	A	A	C	A
Ethylene Oxide	-	A	-	A	-	-	-	A	-	-	D	D	D	C
Fatty Acids	A	A	A	C	-	D	-	A	B	A	A	C	C	C
Nitric Acid (10% Solution)	A	A	A	D	-	D	D	A	B	A	A	D	-	B
Nitric Acid (20% Solution)	A	A	A	D	-	D	-	A	B	A	A	D	-	D
Nitric Acid (50% Solution)	A	A	A	D	-	D	-	A	C	D	A	D	-	D
Nitric Acid (Concentrated Solution)	D	B	A	D	D	D	-	A	D	D	B	D	-	D
Sodium Hydroxide (20%)	A	A	A	C	D	A	-	A	B	A	A	A	D	A
Sodium Hydroxide (50% Solution)	A	B	A	C	D	B	-	A	C	A	D	D	D	-
Sodium Hydroxide (80% Solution)	A	D	A	C	D	C	-	A	C	A	B	D	D	-



**S4S CO., LTD**  
 SUPPLY FOR SUCCESS

+84 389 850 950  
 +84 913 873753  
 doanmau.linh@s4s.vn  
 +84 913873753  
 www.s4s.vn




**S4S CO., LTD**  
 SUPPLY FOR SUCCESS



**SCAN ME**

**NHIỆT ĐỘ LÀM VIỆC CỦA VẬT LIỆU LÀM KÍN**

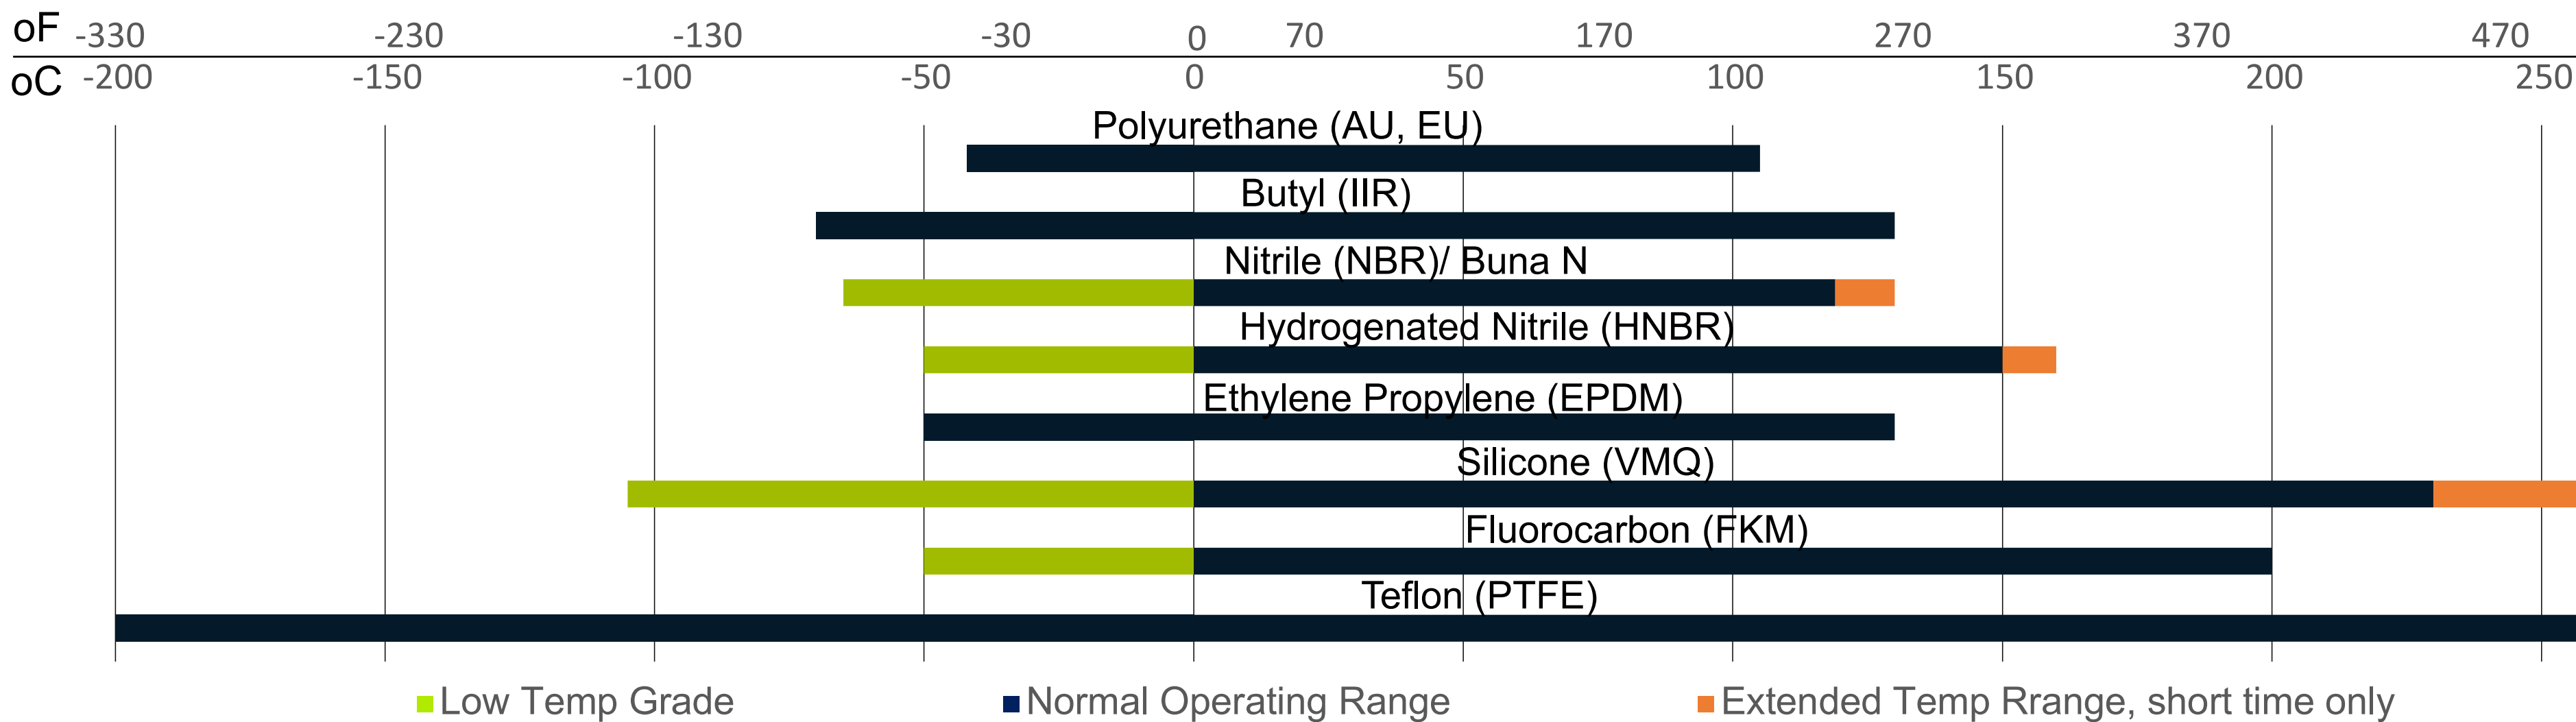

**VẬT LIỆU LÀM KÍN**

